

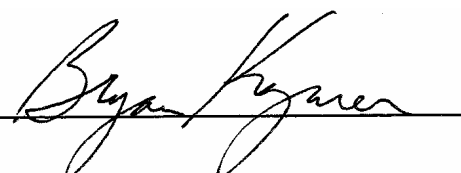
LABORATORY TEST REPORT

COMPOUND: Sevrene® 4120-64A
COLOR: N/A
SPECIFICATION: GENERAL

PAGE: 1 of 1

DATA REPRESENTS ACTUAL LABORATORY TESTS

Test Method	Results
1. Hardness, ISO 868 Shore "A"	59
2. Specific Gravity, ISO 1183 Water Immersion	.910
3. Tensile Strength ISO 37; MPa	8.0 MPa
4. Elongation% @ break ISO 37; %	706%
5. Modulus @ 100% ISO 37	1.8 MPa
6. Tear Strength ISO 34: Kn/m	26.3 kN/m

Approved by: 

* Test is outside our scope of accreditation.

** This test was performed by a subcontracted accredited testing laboratory.

*** This test was performed at supplier's biological laboratory.

O:\2010\418_Sevrene4120-64A_General.doc

All tests are performed once.

This report is not to be reproduced except in full.